


TENSILE REPORT

Product: Ø8 CB240T
According to TCVN 1651-1:2008

Lot No: 16031711
Test Date: 17/03/2016

No.	Diameter mm	Gauge mm	Elongation mm	Area mm ²	Yield load kN	Yield Strength MPa	Tensile Load kN	Tensile Strength MPa	Elongation %
1	8	80	48.2	50.3	15.3	305	23.3	463	60.2
2	8	80	45.8	50.3	15.4	306	23.7	472	57.2
3	8	80	59.2	50.3	16.8	334	23.7	472	74.0
Average	8	80	51.1	50.3	15.8	315	23.6	469	63.8

TEST CHART

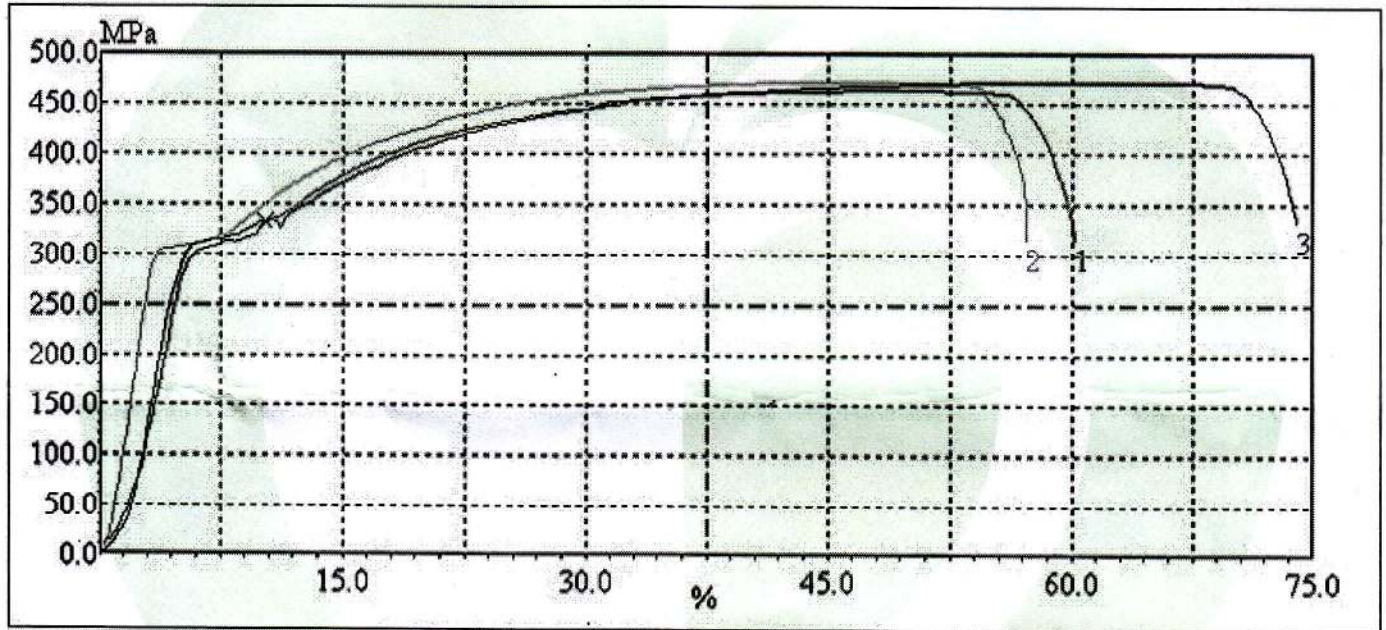

BEND REPORT

Test No.	Bending angle	Plunger diameter	Test result
1	180 degrees	16 mm	No crack
2	180 degrees	16 mm	No crack
3	180 degrees	16 mm	No crack
Average	---	---	---

Operator

QC Manager



Võ Văn Hiếu